



Aalborg Universitet

**AALBORG UNIVERSITY**  
DENMARK

## Effect of Crystallisation Degree on Hardness of Basaltic Glass-Ceramics

Jensen, Martin; Smedskjær, Morten Mattrup; Yue, Yuanzheng

*Publication date:*  
2010

*Document Version*  
Early version, also known as pre-print

[Link to publication from Aalborg University](#)

*Citation for published version (APA):*

Jensen, M., Smedskjær, M. M., & Yue, Y. (2010). *Effect of Crystallisation Degree on Hardness of Basaltic Glass-Ceramics*. Poster presented at 22nd International Congress on Glass, Salvador, Brazil.

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

### Take down policy

If you believe that this document breaches copyright please contact us at [vbn@aub.aau.dk](mailto:vbn@aub.aau.dk) providing details, and we will remove access to the work immediately and investigate your claim.

# Effect of Crystallisation Degree on Hardness of Basaltic Glass-Ceramics

Martin Jensen\*, Morten M. Smedskjaer, Yuanzheng Yue

Section of Chemistry, Aalborg University, Denmark

\* Corresponding author. Tel.: +45 99407246. E-mail: maj@bio.aau.dk

## Introduction

Hardness is important for wear resistance and abrasiveness in glass-ceramics


As hardness of inorganic crystals is determined by their bond strength and atomic structure<sup>1</sup>, it is likely that hardness of glass-ceramics changes with heat treatment conditions

Measure crystallisation degree by 3 different techniques: 1) Processing of images acquired by means of optical microscopy; 2) X-ray diffraction (XRD); 3) Differential scanning calorimetry (DSC). 1 and 2 provide absolute crystallisation degree  $D_{c,abs}$  whereas 3 gives relative one  $D_{c,rel}$


Heat treatment of the glass for 30 min at 730-1084 °C

## Crystallisation Degree

Leaf-like crystals identified as augite are found. The size of the crystals increases with heat treatment temperature ( $T_h$ ). After etching, traces of a mica phase were also found at  $T_h < 1010$  °C<sup>2</sup>.

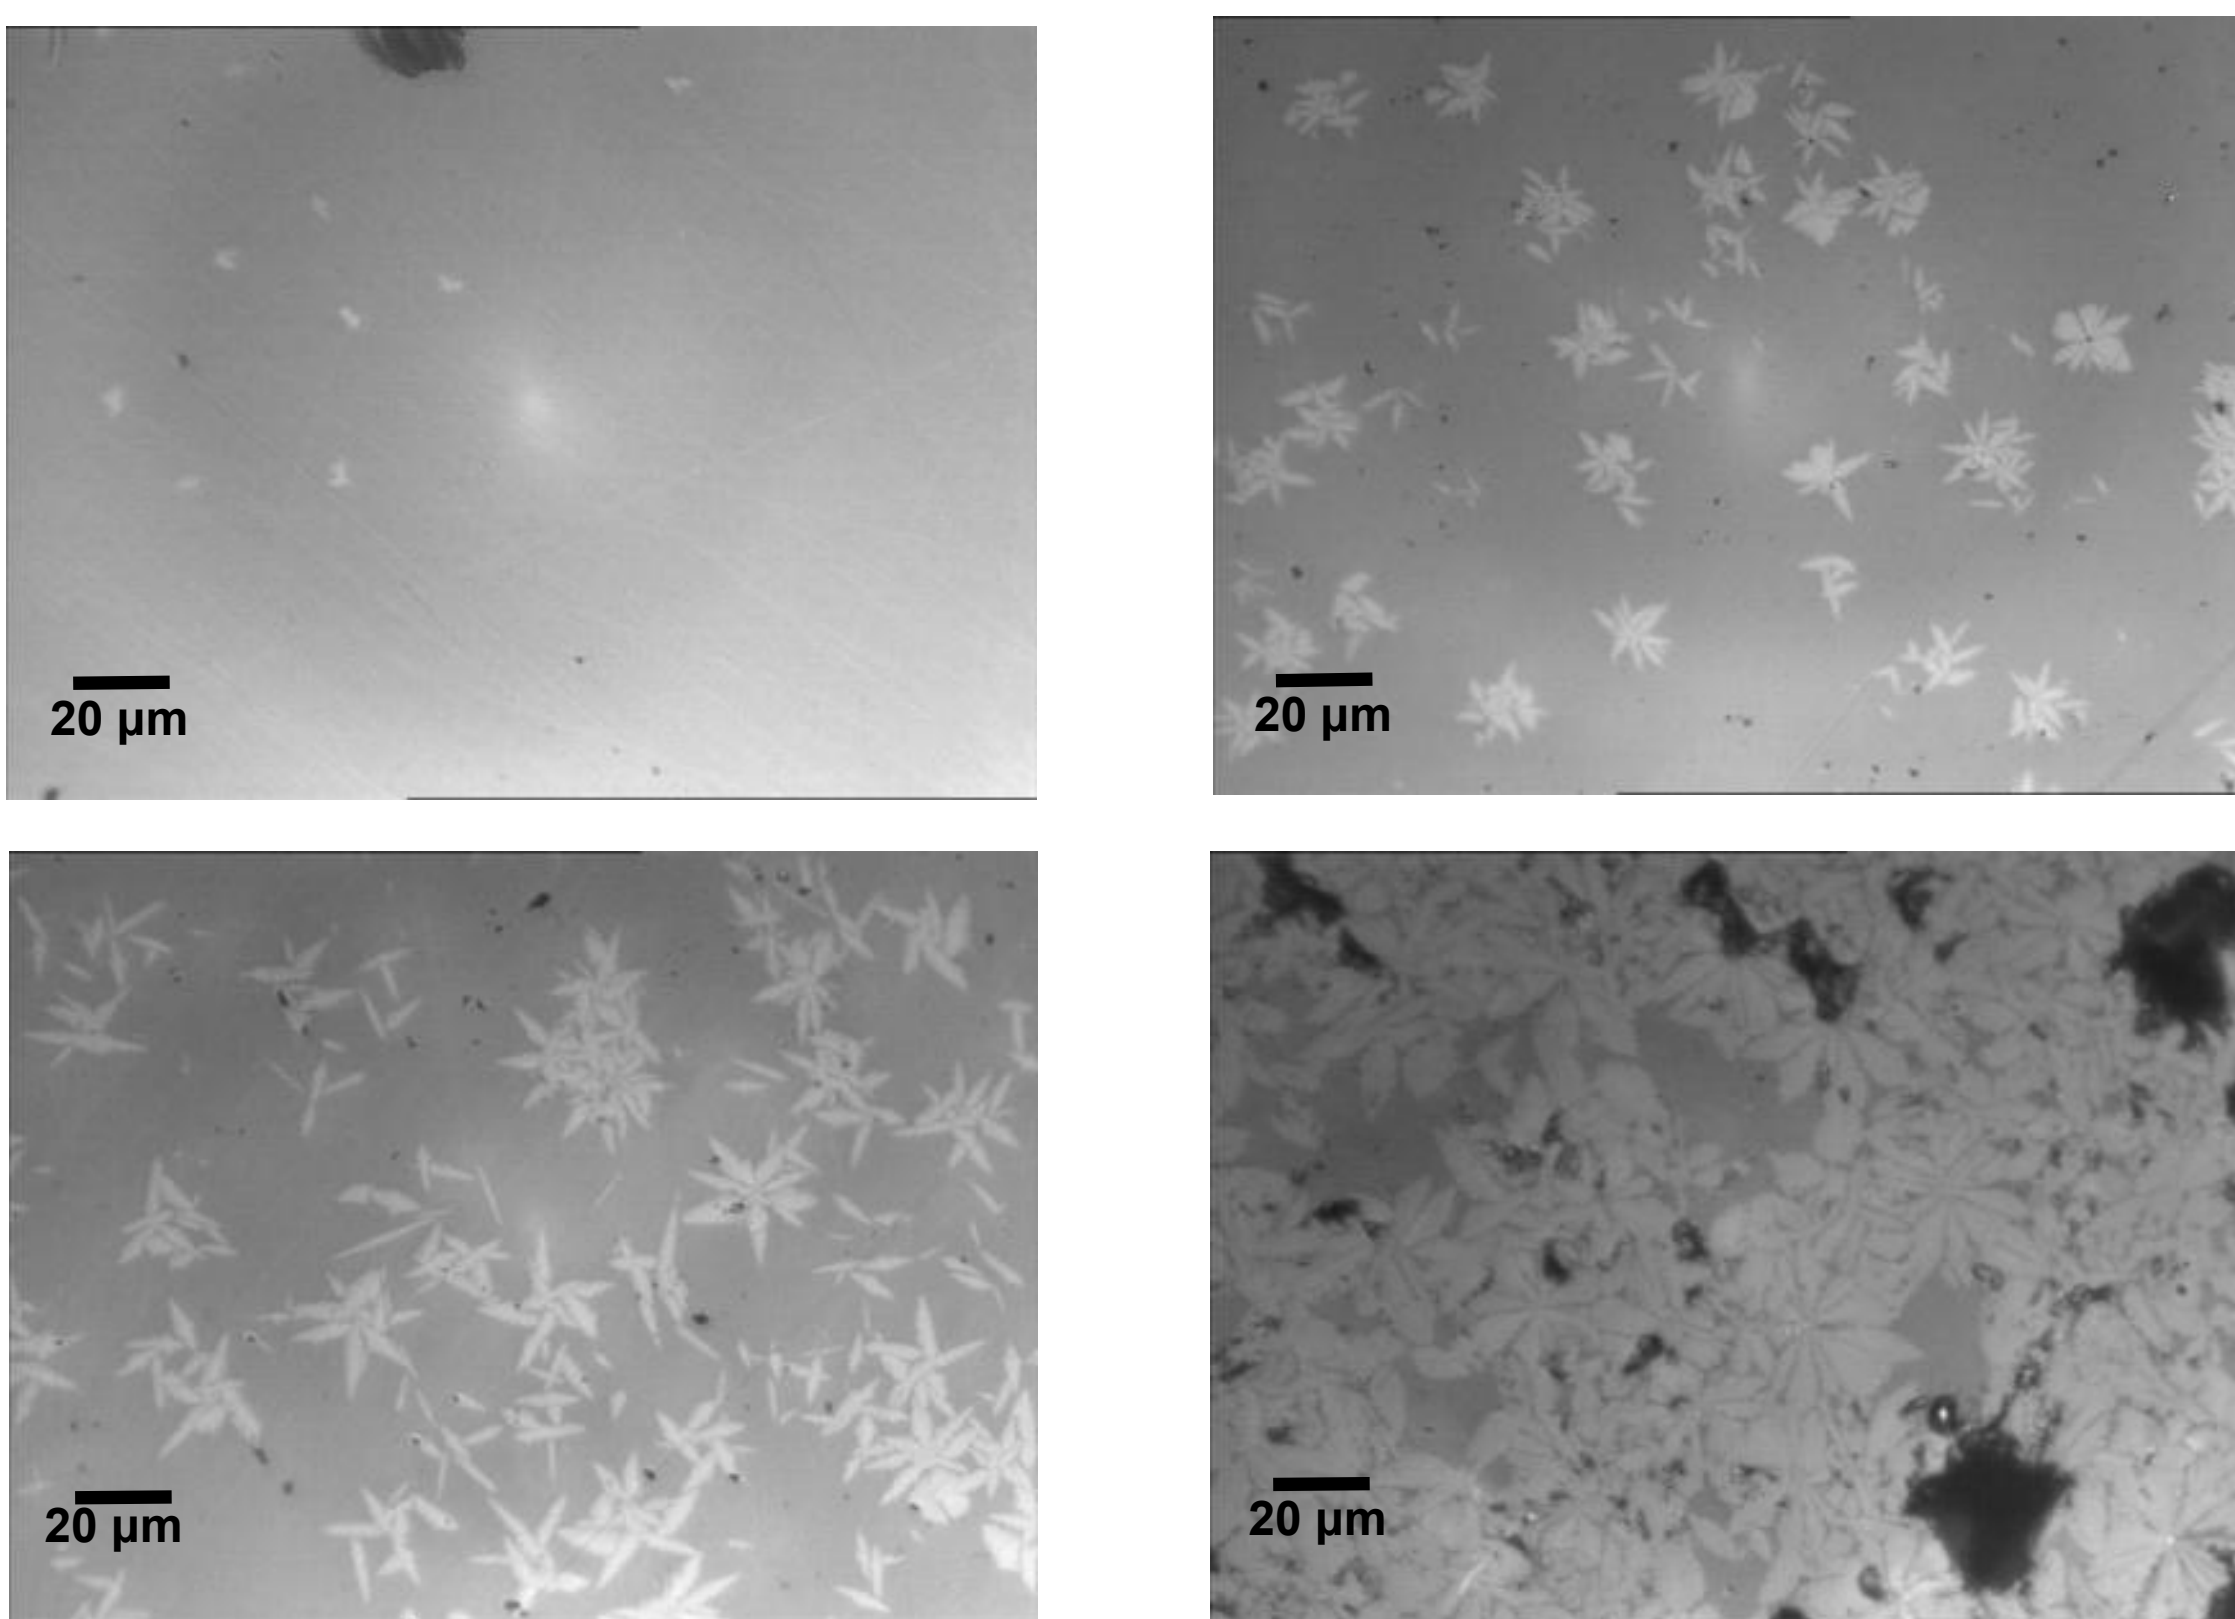


Only DSC could detect the mica crystals, which leads to the discrepancy between the curves at low  $T_h$ . Augite crystallises around 910 °C. The crystallisation degree has an S-shaped behaviour as a function of heat treatment temperature

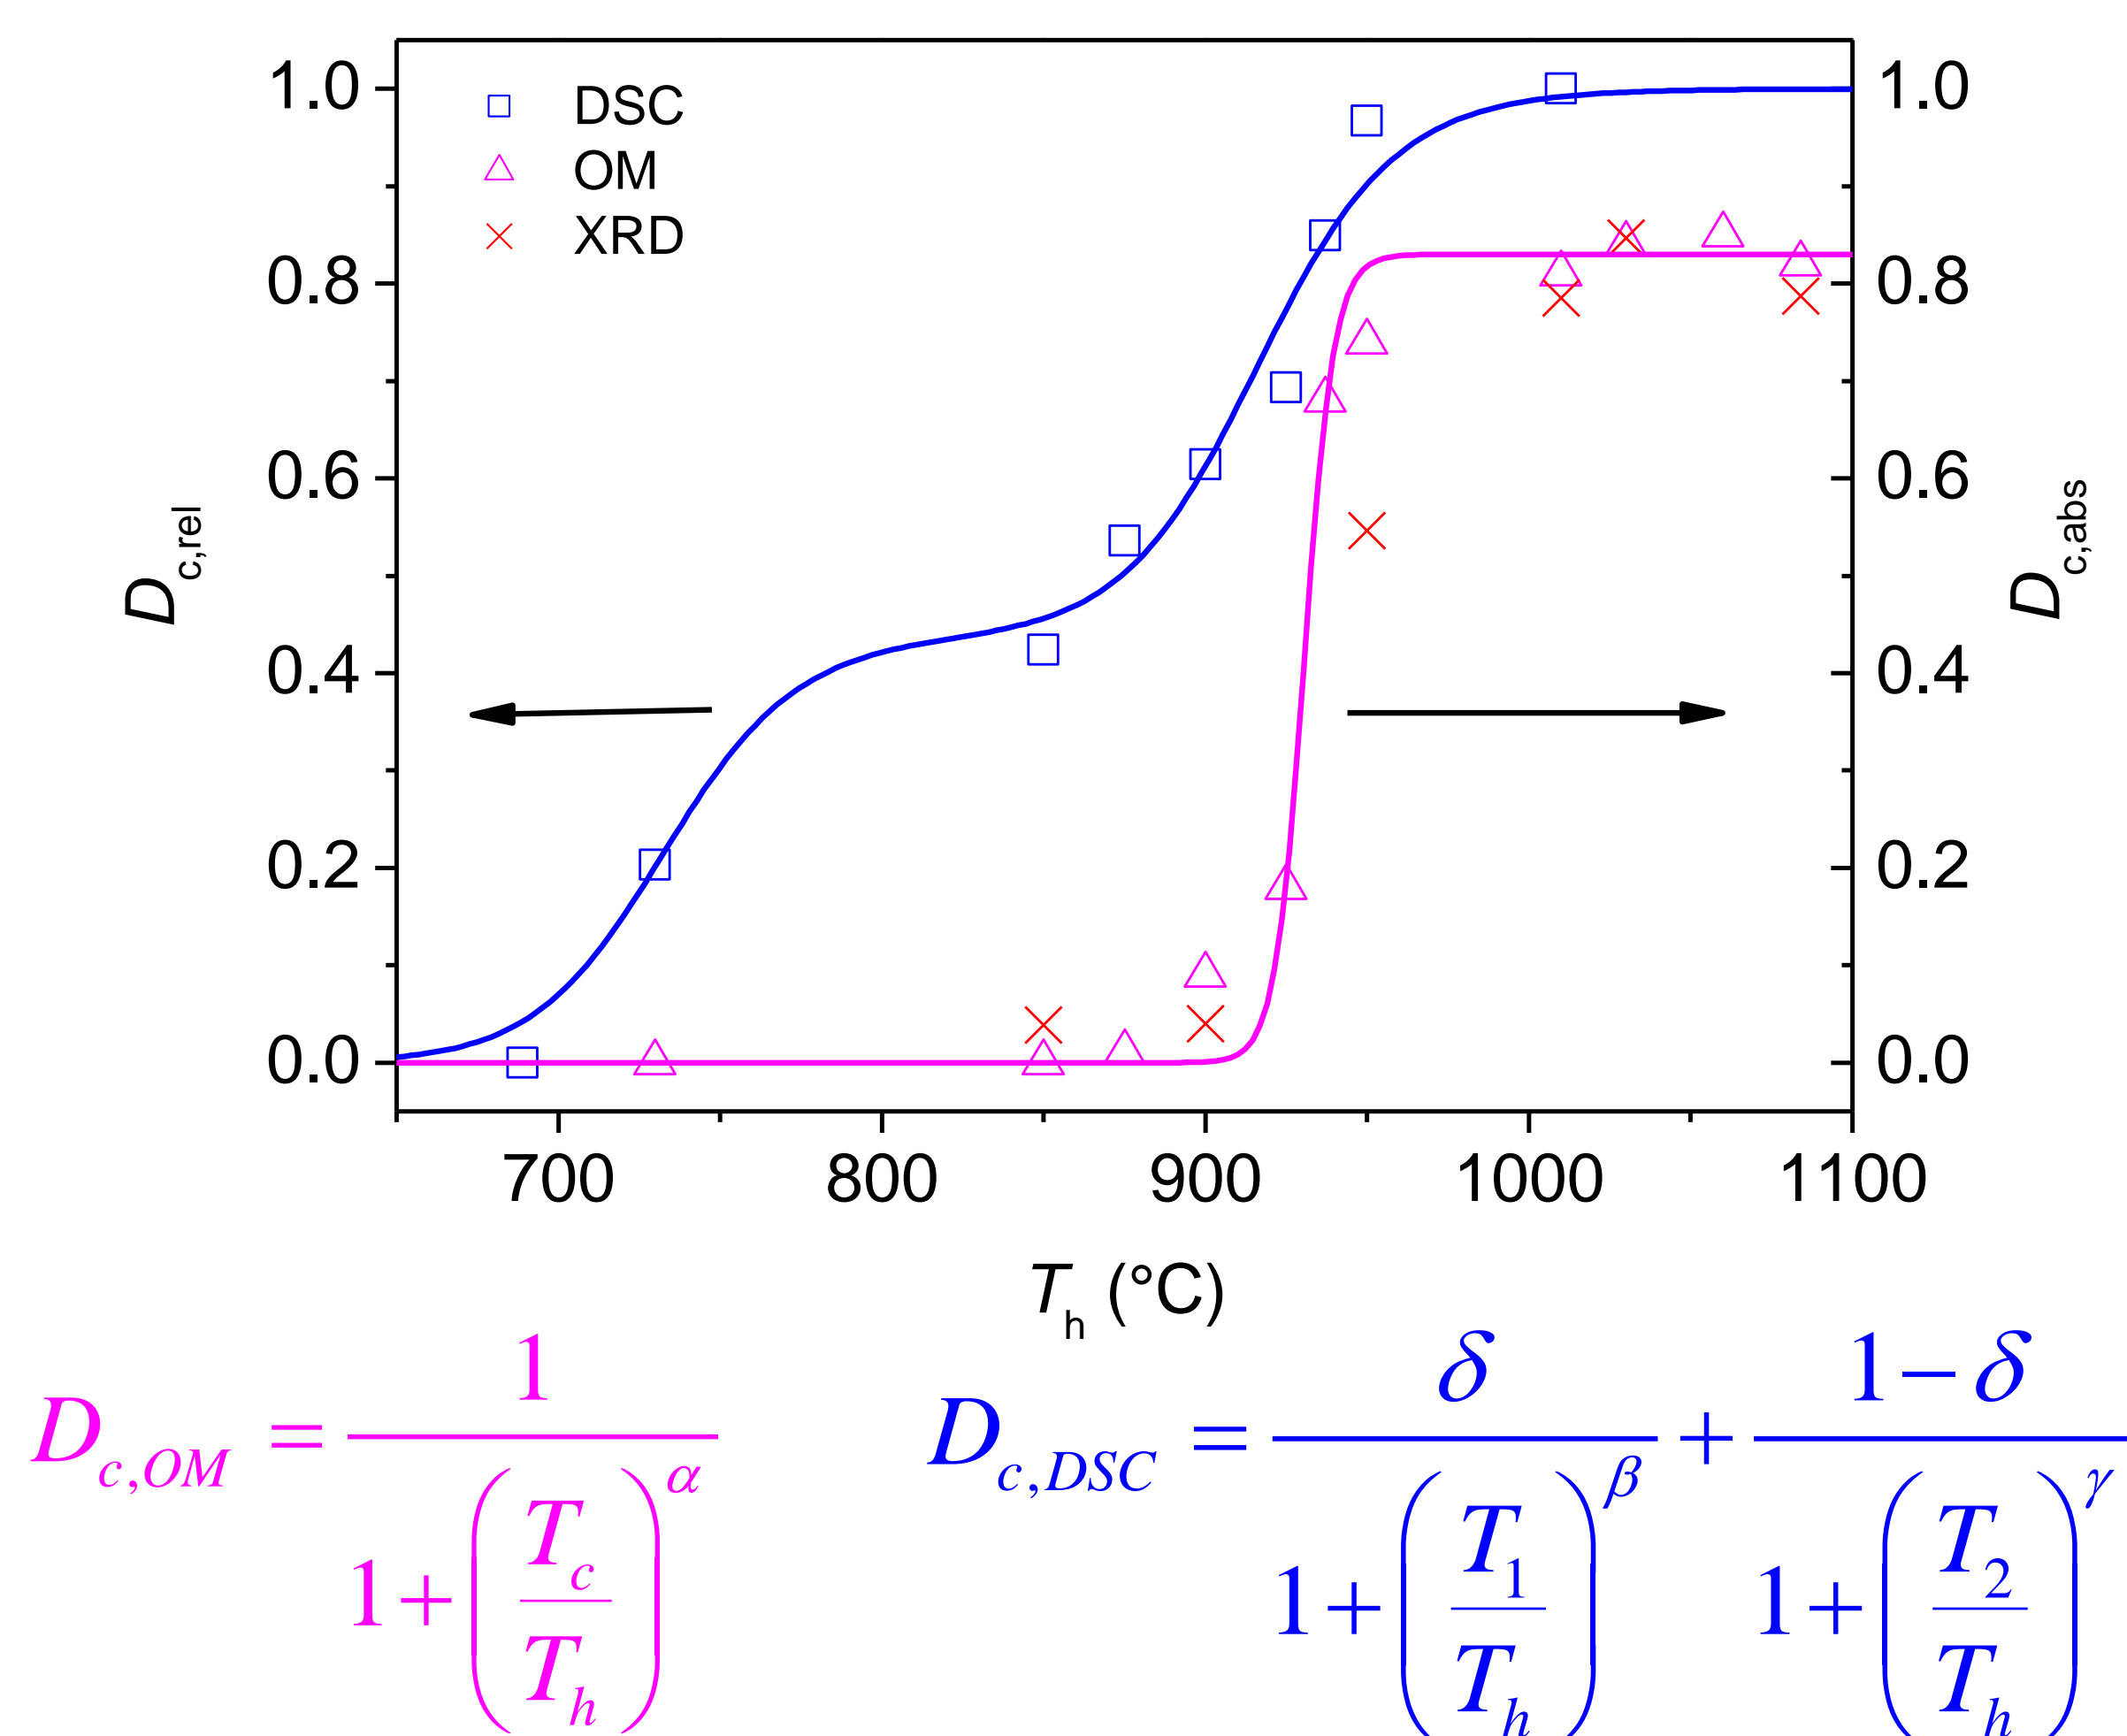


## Hardness

Hardness measured of both glass/mica and augite phase. The hardness of the glassy phase decreases slightly whereas that of the augite phase shows a more pronounced decrease when the heat treatment temperature is elevated. The hardness of the crystal phase is higher than that of the glassy one

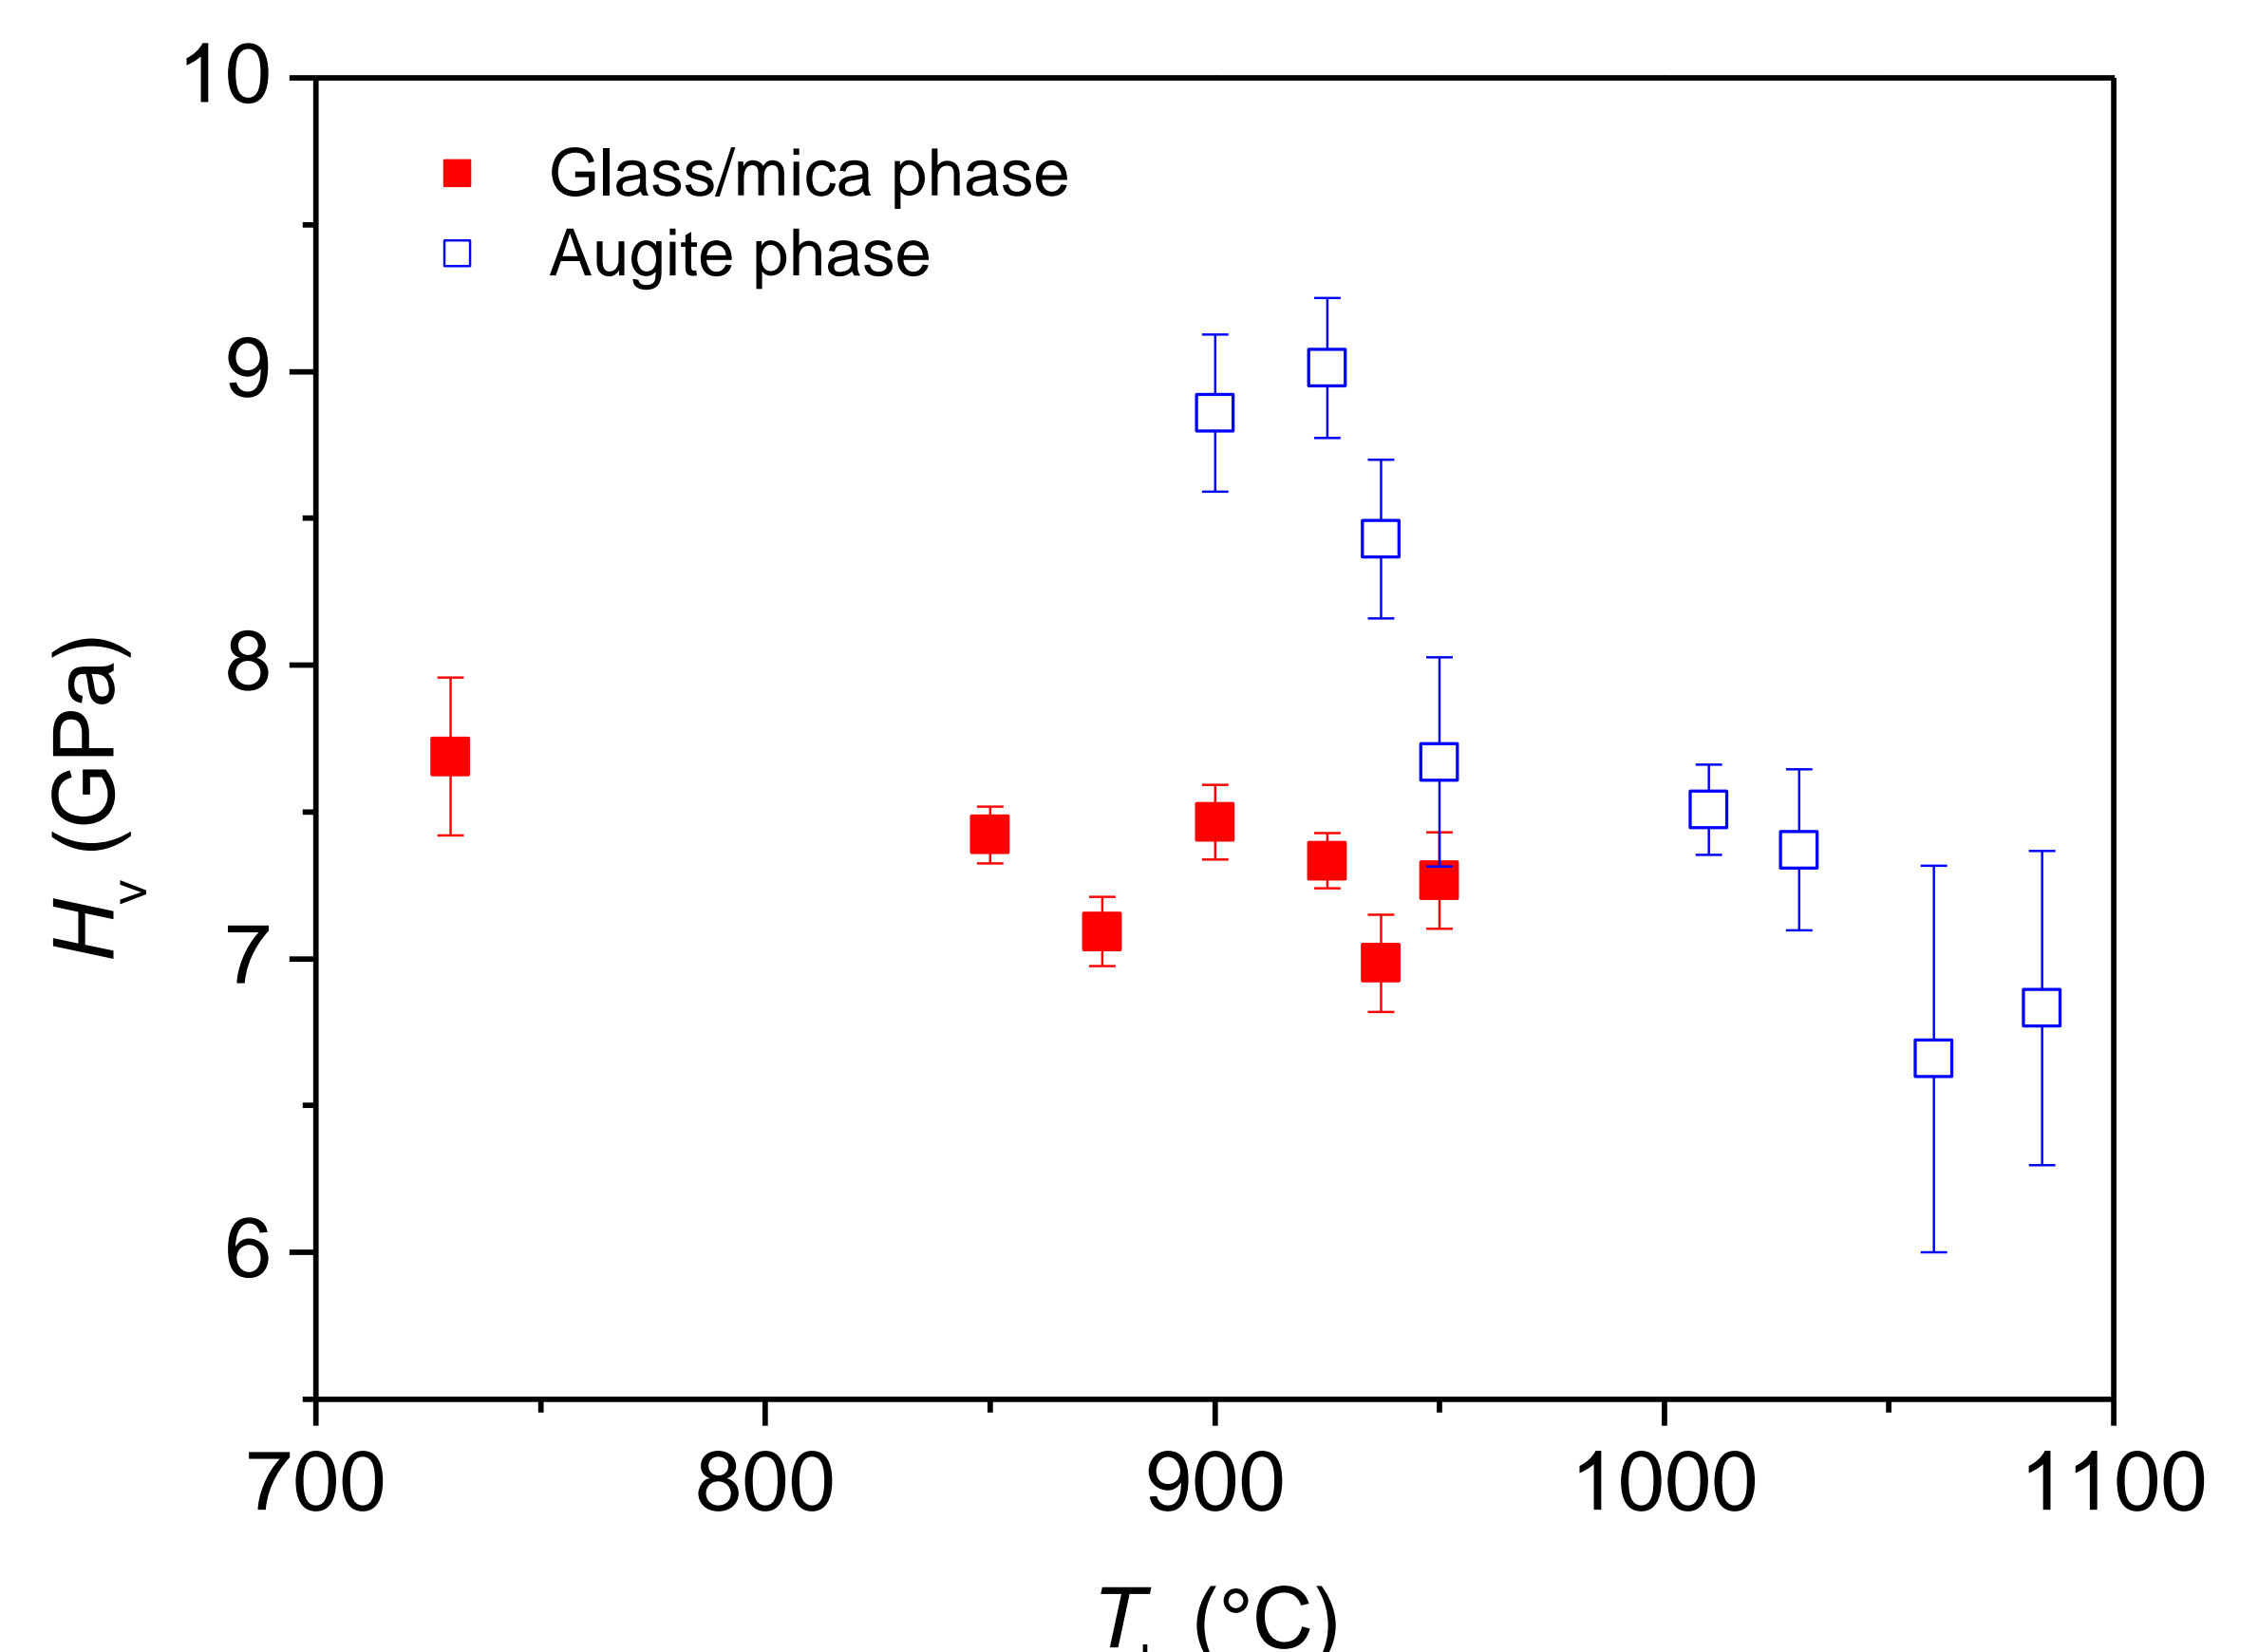

As only DSC can detect both mica and augite crystals, hardness is plotted against the crystallisation degree determined by DSC. The decreasing hardness of the crystalline phase as a function of heat treatment temperature can partly be described by the Hall-Petch relationship.

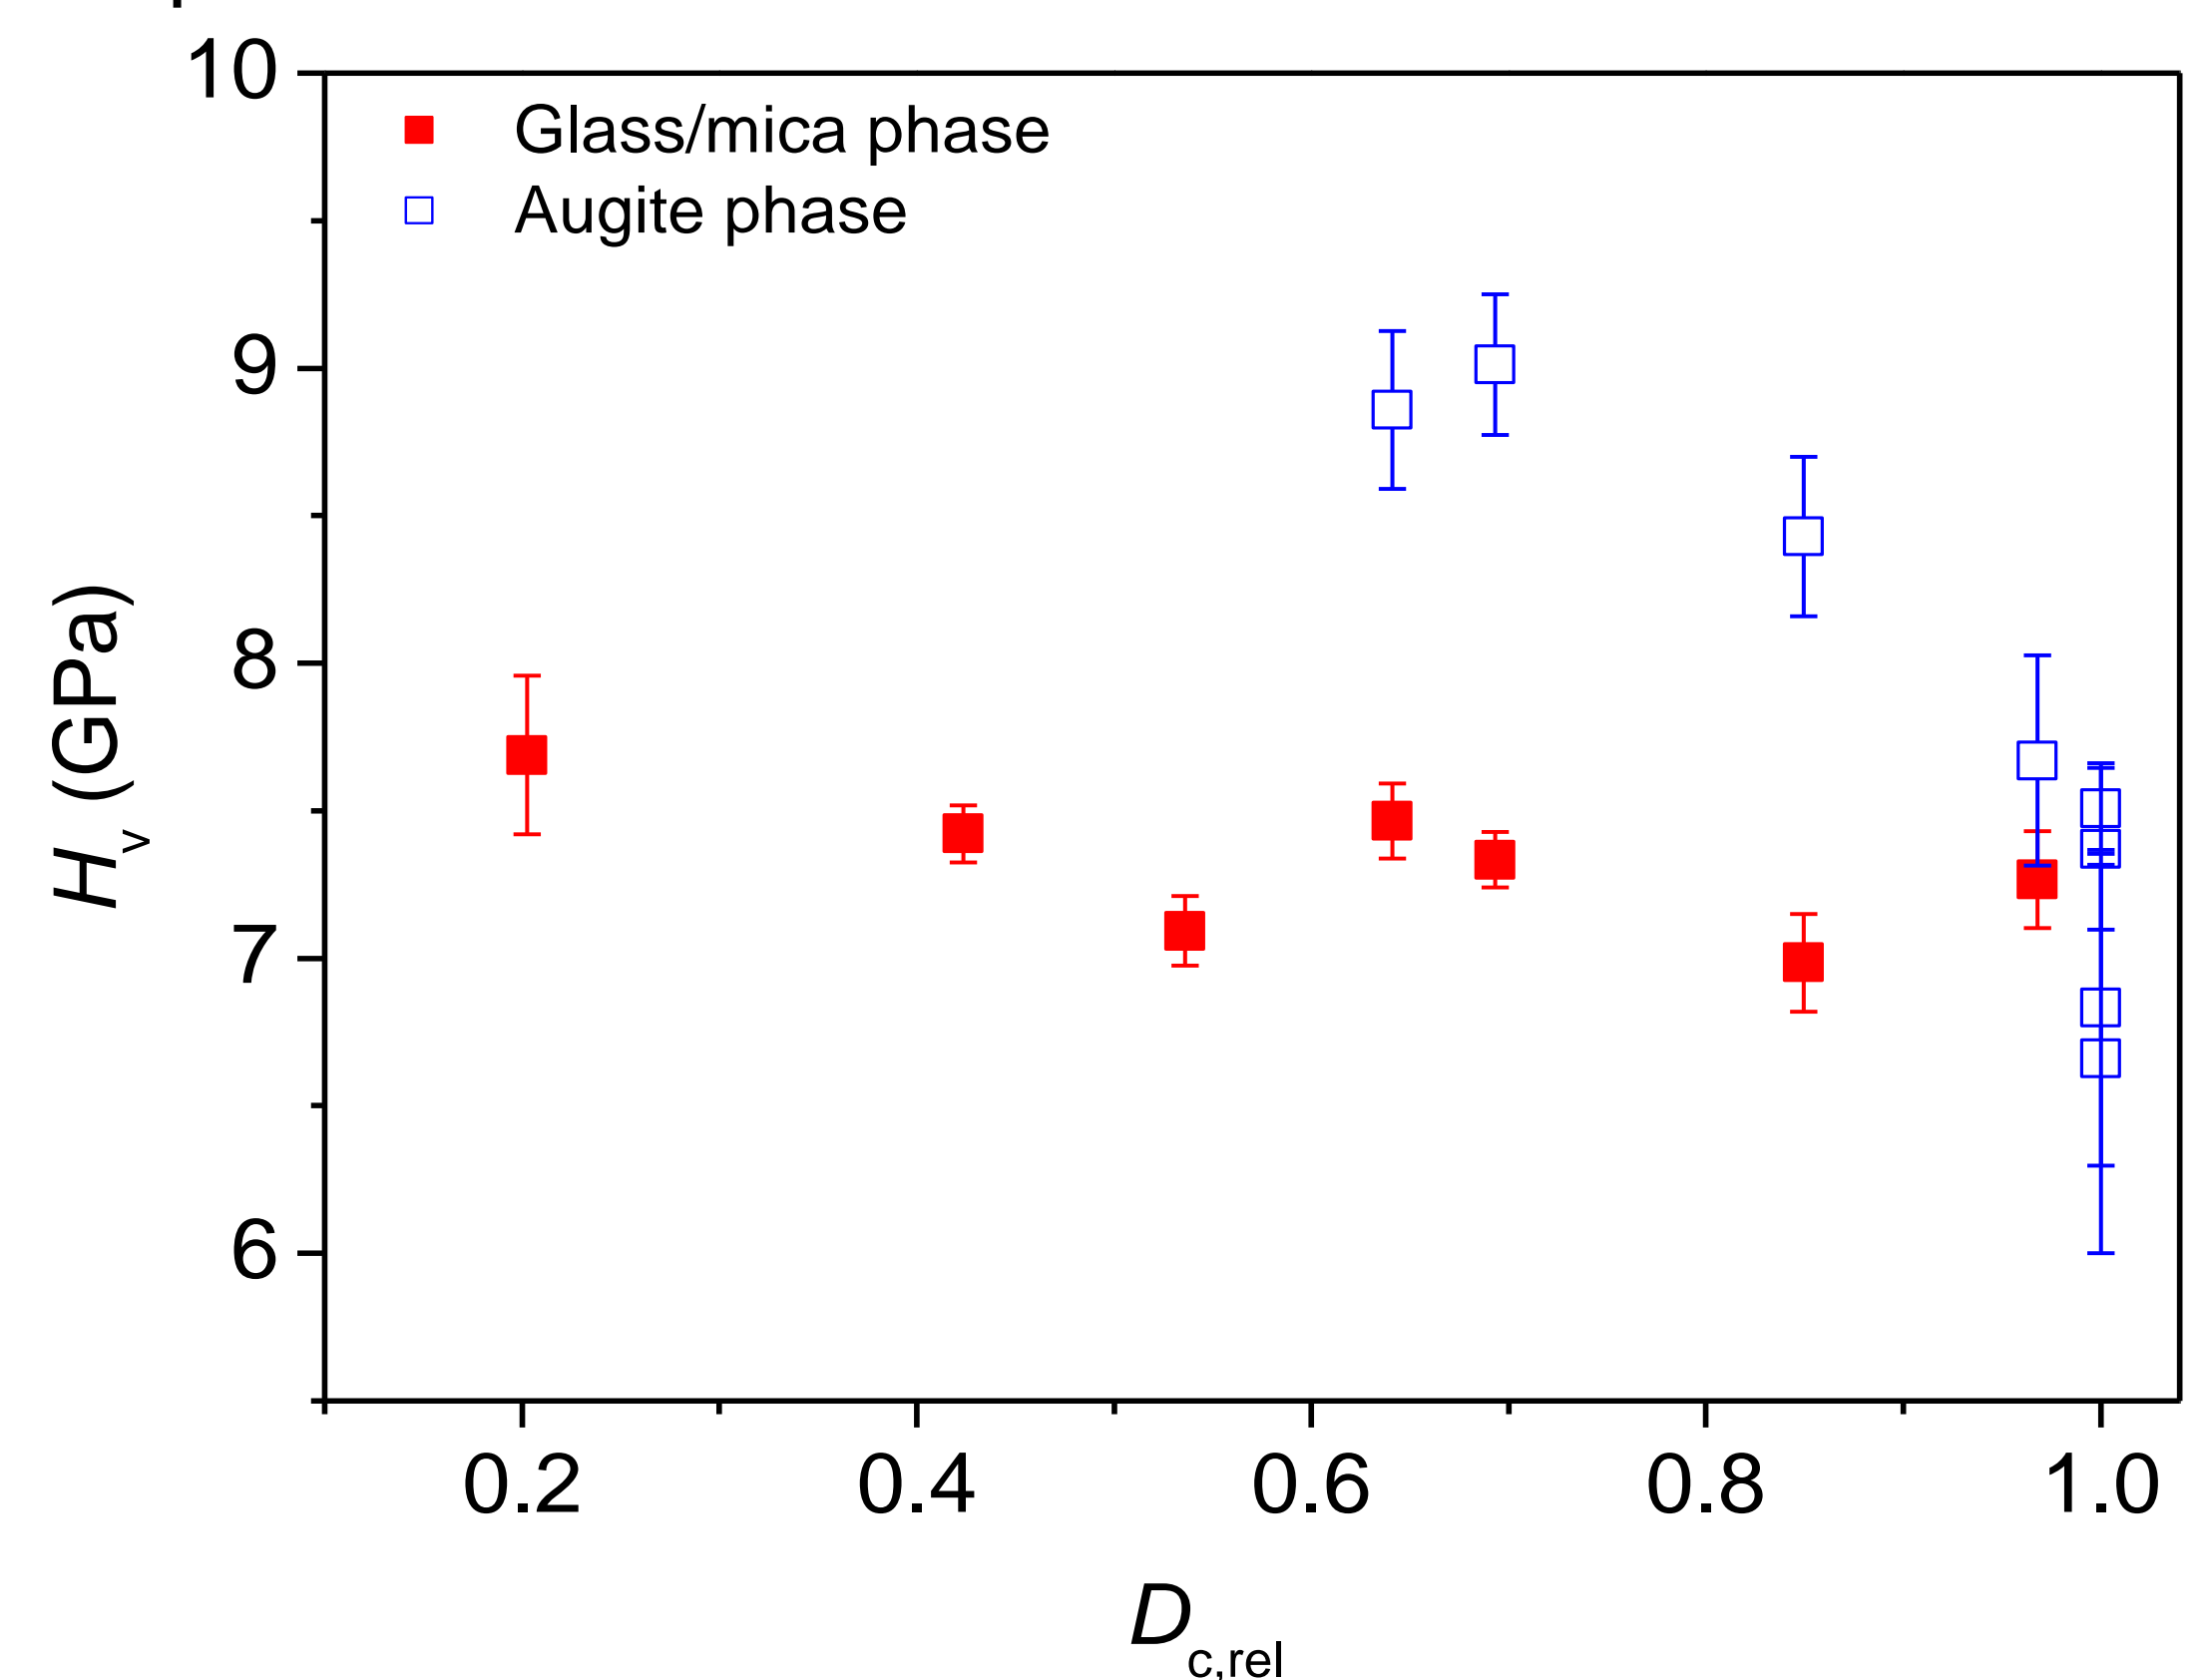

## Conclusions

- 1) During heat treatment of basaltic glass both mica and augite crystals form
- 2) The hardness of the glass and augite phase decrease when the heat treatment temperature is increased
- 3) The highly crystallised glass-ceramic has a lower hardness than the less crystallised one

## References

- 1 F. M. Gao et al. (2003) *Phys. Rev. Lett.* **91**, 015502
- 2 M. Jensen et al (2009) *Glass Technol.: Eur. J. Glass Sci. Technol. A*, **50**, 189